

Article

111In-labeled glycoprotein non-metastatic b (GPNMB) targeted gemini surfactant-based nanoparticles against melanoma: In vitro characterization and in vivo evaluation in melanoma mouse xenograft model

Amal Makhoulf, Istvan Hajdu, Siddesh v Hartimath, Elahe Alizadeh, Kayla Wharton, Kishor M. Wasan, Ildiko Badea, and Humphrey Fonge

Mol. Pharmaceutics, **Just Accepted Manuscript** • DOI: 10.1021/acs.molpharmaceut.8b00831 • Publication Date (Web): 03 Jan 2019

Downloaded from <http://pubs.acs.org> on January 4, 2019

Just Accepted

"Just Accepted" manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides "Just Accepted" as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. "Just Accepted" manuscripts appear in full in PDF format accompanied by an HTML abstract. "Just Accepted" manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). "Just Accepted" is an optional service offered to authors. Therefore, the "Just Accepted" Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the "Just Accepted" Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these "Just Accepted" manuscripts.



ACS Publications

is published by the American Chemical Society, 1155 Sixteenth Street N.W., Washington, DC 20036
Published by American Chemical Society. Copyright © American Chemical Society. However, no copyright claim is made to original U.S. Government works, or works produced by employees of any Commonwealth realm Crown government in the course of their duties.

¹¹¹In-labeled glycoprotein non-metastatic b (GPNMB) targeted gemini surfactant-based nanoparticles against melanoma: *In vitro* characterization and *in vivo* evaluation in melanoma mouse xenograft model

Amal Makhoul^{a,b}, Istvan Hajdu^a, Siddesh V. Hartimath^{c,d}, Elahe Alizadeh^{c,d}, Kayla Wharton^a, Kishor M. Wasan^a, Ildiko Badea^a and Humphrey Fonge^{c,d,e*}

^aDrug Discovery and Development Research Group, College of Pharmacy and Nutrition, University of Saskatchewan, 107 Wiggins Road, Saskatoon, SK, S7N 5E5, Canada

^bDepartment of Pharmaceutics and Industrial Pharmacy, Faculty of Pharmacy, Cairo University, Kasr El-Aini, 12411, Cairo, Egypt

^cDepartment of Medical Imaging, College of Medicine, University of Saskatchewan 103 University Drive, Saskatoon, SK, S7N 0W8, Canada

^dSaskatchewan Centre for Cyclotron Sciences (SCCS), the Fedoruk Centre, Saskatoon SK, Canada, 120 Maintenance Rd, Saskatoon, SK, S7N 5C4, Canada

^eDepartment of Medical Imaging, Royal University Hospital Saskatoon, SK, 103 University Drive S7N 0W8, Canada

Author for correspondence

*Humphrey Fonge, PhD
103 Hospital Dr.

1
2
3 Department of Medical Imaging
4

5
6 RUH Saskatoon, Saskatoon SK, S7N 0W8
7

8
9 Canada
10

11 Email: humphrey.fonge@usask.ca
12

13
14 Tel: 306-655-3353
15

16
17 Fax: 306-655-1637
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Abstract

Melanoma is a devastating form of skin cancer with high tendency to metastasis. This work addresses the development of new targeted nanoparticles that can be used for SPECT imaging of melanoma. Melanoma-specific glycoprotein non-metastatic b (GPNMB) antigen targeted and non-targeted gemini nanoparticles were prepared, characterized and radiolabeled with ^{111}In . ^{111}In -labeled nanoparticles comprised of gemini surfactant grafted with monoclonal antibody Fab fragment that targets GPNMB. Specific uptake of GPNMB-Fab was studied in six melanoma cell lines using flow cytometry. *In vitro* cellular uptake and internalization was studied using flow cytometry, confocal laser scanning microscopy and radiometric techniques. Specific uptake of anti-GPNMB targeted nanoparticles was observed in GPNMB expressing cells which was higher than low expressing or control cells. *In vitro* studies showed that conjugation of GPNMB targeted nanoparticles led to enhanced intracellular uptake of the nanodelivery system which is critical for drug delivery. *In vivo* distribution of the nanoparticles was studied by microSPECT/CT imaging and *ex vivo* biodistribution. Tumor uptake was significantly higher ($p < 0.05$) in non-targeted nanoparticles (5.47 ± 0.46 %IA/cc) compared to GPNMB targeted nanoparticles (1.87 ± 0.27 %ID/cc), which might be attributed to the high spleen uptake of the targeted formulation. These findings demonstrated that the radiolabeled gemini nanoparticles are promising for image-guided radiotherapy of melanoma. Formulation optimization is needed to improved tumor uptake and *in vivo* intracellular delivery for radiotherapeutic applications.

Key words: GPNMB Nanoparticles; Theranostics; ^{111}In Indium; Gemini; Melanoma; Imaging

Introduction

Melanoma is the deadliest form of skin cancer due to its high propensity of metastasis and limited treatment options. The rise in the incidence of melanoma in the last 50 years is the highest among all cancers¹. The five-year survival rates for melanoma that has metastasize to lymph nodes or other organs is 17%². Early diagnosis and surgery are the patients' best hope for managing early stages of melanoma. The median progression-free survival for the FDA-approved pembrolizumab, while better than other therapies, is 5.5 months which is lower than the same treatment in lung cancer (6.3 months)³. Two approaches could reduce melanoma morbidity and mortality: early detection and the development of novel therapies to expand the current arsenal.

Novel nanoparticle formulations could address both areas: development of sensitive diagnostic tools and targeted delivery of curative agents. Enhanced permeability and retention effect (EPR) allows extravasation of the nanoparticles into the tumour through the leaky vasculature, leading to their preferential accumulation compared to healthy tissue⁴. In addition, nanoparticles might bypass certain uptake barriers such as epithelial tight junction⁵. Nanoparticles can be functionalized with targeting peptides and radionuclides for use as diagnostics and targeted radiotherapeutics⁶. Imaging and therapeutic radionuclides can be effectively delivered to tumor site by functionalized nanoparticles, thus improving imaging quality and therapeutic efficiency⁷. Our research group focuses on the design and synthesis of gemini surfactants to build drug delivery nanoparticles^{8,9}. Gemini surfactants, N,N-bis(dimethylalkyl)- α,ω -alkanediammonium halide derivatives, have been shown to be attractive in the drug delivery field¹⁰. They are simply two surfactants chemically connected by a spacer. The physicochemical properties of these compounds can be modulated by the modification in the structure of the alkyl tails and the spacer groups. Alteration of the alkyl chain length, substitution of different functional groups and the degree of

unsaturation provide the possibility to tailor specific compounds for a certain need ⁹. Gemini surfactants self-assemble into nanoparticles, which adopt various morphologies (micelles, inverted micelles, liposomes, cubosomes) to deliver small and large molecules and radionuclides to tumor cells ¹⁰.

Monoclonal antibody against glycoprotein NMB (GPNMB) was selected as a targeting vector. GPNMB is a 560-amino acid glycosylated transmembrane protein structurally similar to pMEL-17, a melanocyte specific marker that is specifically expressed in melanoma cells ¹¹. Compared to healthy cells, tumours such as breast cancer, melanoma and glioblastoma overexpress GPNMB, presenting a new class of targets for these types of cancer ^{12,13}. Overexpression of GPNMB promotes metastasis, reduces cells apoptosis and increases angiogenesis in tumors ¹⁴. Glembatumumab vedotin, an antibody drug conjugate of anti-GPNMB antibody and antimitotic agent monomethyl auristatin E, is in clinical trials for melanoma and breast cancer ^{15,16,17}. However, the results have not been promising. A subgroup analysis (involving a small number of patients) of a phase II trial in triple negative breast cancer (TNBC) patients whose tumors overexpress GPNMB showed an advantage of glembatumumab vedotin over capecitabine (Xeloda®) ^{16,17}. However, a recent pivotal phase IIb study in a large cohort of TNBC patients whose tumors overexpress > 25% of GPNMB, failed to show an advantage of glembatumumab vedotin over capecitabine ¹⁸. Unlike antibodies/ADCs against other antigens such as epidermal growth factor receptor II (HER 2) where the interaction of the antigen with other receptors has been shown to be responsible for poor response in some patients, the interaction of GPNMB with other receptors has not been well studied. Another factor responsible for poor efficacy of antibody drug conjugates is the presence of drug efflux pump multidrug resistance gene ¹⁹.

¹¹¹In was selected as the imaging radionuclide as its physical decay ($t_{1/2}$ 2.8 days) is ideally suited for single-photon emission computed tomography (SPECT) imaging of long circulating nanodelivery systems. SPECT imaging has high sensitivity and good spatial resolution, and it is becoming an indispensable technique for *in vivo* imaging ²⁰. In this study we have used ¹¹¹In to evaluate the *in vivo* properties of the nanodelivery system. The rationale for the choice of DOTA as chelating agent is that it can be used for imaging (with ¹¹¹In) and subsequently for alpha particle therapy (actinium-225: ²²⁵Ac) for alpha particle radiotherapy. This allows us to use ¹¹¹In as a surrogate to understand the *in vitro* and *in vivo* characteristics of the nanodelivery system. Alpha particle therapy causes irreversible DNA double-strand break due to its high linear energy transfer (LET), approximately 25-230 kEv/ μ m, which is about 100 to 1000 times the average LET of beta particles ²¹. The overall goal of the study was to develop and evaluate an ¹¹¹In-labeled germini surfactant nanodelivery system containing anti-GPNMB fab fragment in cells and mouse models of GPNMB overexpressing melanoma.

Materials and methods

Materials

Anti-GPNMB therapeutic antibody (glembatumumab) Fab (GPNMB-Fab) was purchased from Creative Biolabs NY, USA). Helper lipid 1, 2 dioleoyl-*sn*-glycero-phosphatidylethanolamine (DOPE), 1,2 Dipalmitoyl-*sn*-glycero-phosphocholine (DPPC) and 1,2 Distearoyl-*sn*-glycero-phosphocholine (DSPC) were purchased from Avanti Polar Lipids (Alabaster, AL).

¹¹¹In was purchased from Nordion Inc. (Ottawa, ON). Activity measurements were made using a Biodex Atomlab 500 Dose Calibrator (Shirley, NY). For accurate quantification of activities, samples were counted for 1 min on a calibrated Perkin-Elmer Automatic Wizard2

Gamma Counter (Waltham, MA). Labeling of nanoparticles with ^{111}In was monitored using silica-gel impregnated glass-fiber instant thin layer chromatography (iTLC) paper (Agilent Technologies, Santa Clara, CA).

Formulation of gemini surfactant nanoparticles

Lipid film hydration method was adopted to prepare gemini nanoparticles using DOPE, DPPC or DSPC as helper lipids. A homogenous lipid film was obtained by dissolving gemini surfactant, DOPE and DSPC or DPPC in anhydrous ethanol with the aid of sonication at room temperature for 10 minutes. Ethanol was then removed by evaporation under reduced pressure at 50 °C using rotavap (BÜCHI Heating Bath B-490, vacuum pump V-700, Flawil). The lipid film was stored in -80 °C for 12 h and freeze dried using Labconco® Freezone Plus 6 L cascade freeze dryer, MO, USA at -80 °C and 0.03 mBar pressure for 24 h to remove ethanol residues. Nanoparticles are formed by hydration of the lipid film using isotonic sucrose solution (9.25 %) in phosphate buffered saline of pH 7.4 (PBS) (HyClone™, Hyclone Laboratories, Logan UT). Lipid film hydration was performed by ultrasonication (Elma ultrasonic, Singen) at 50 °C for two hours. The obtained nanoparticle suspension was filtered through Acrodisc® 0.45 µm syringe filter (Pall Gelman, Ann Arbor, MI). Table 1 summarizes the composition of the prepared gemini nanoparticles. In all analyses, triplicate batches of each formulation were evaluated.

Characterization of gemini surfactant nanoparticles

The size and zeta-potential of the particles were measured using Zetasizer Nano ZS instrument (Malvern Instrument, UK). Results are reported as the mean of 3 – 5 measurements ± standard deviation. Aliquots of 10 µL samples were dropped onto 300-mesh formvar-coated copper grids

(SPI Supplies). The water was blotted with absorbent tissue and samples were examined using Philips CM10 electron microscope (Eindhoven, The Netherlands).

Preparation of fluorescent labeled gemini surfactant nanoparticles

The lipophilic marker (DiO; ex/em wavelength 484nm/501nm) was integrated in the lipid film at a final concentration of 0.2 mg/mL of nanoparticle dispersion, while the hydrophilic tracer (FITC-Dextran; ex/em wavelength 492nm/518nm) was dissolved in the hydration solution at concentration of 1 mg/mL. Nanoparticles were prepared applying the same procedures as mentioned before.

Flow cytometry analysis

After initial passage in tissue culture flasks, RPMI-7951 and A375 cells were grown in 6-well plates. When reached 70-80% confluence, the cells were washed with PBS and treated with FBS free medium containing 10% fluorescent gemini nanoparticle dispersion or dye solution in PBS (0.2 mg/mL for Dio and 1 mg/mL for FITC-dextran). After two hours incubation at 37 °C, cells were washed with PBS, collected by trypsinisation, pelleted, washed with 4 mL PBS and resuspended in 500 µL PBS for flow cytometry.

Flow cytometric analysis (FACS analysis) for nanoparticles' fluorescence was performed using a 4-color FACS-Calibur (Becton Dickinson, Heidelberg, Germany) equipped with an argon laser exciting at a wavelength of 488 nm. For each sample, 10000 events were collected by list-mode data that consisted of side scatter, forward scatter and fluorescence emission centered at 530 nm (FL1) for DiO and FITC-dextran. For Alexa Flour® 647 detection, a long-pass filter with a cutoff of 670 nm (FL3) was applied. Cell Quest Pro software (Becton Dickinson, Heidelberg, Germany) was applied for the analyses.

Confocal laser scanning microscopy

For confocal microscopy, the cells were grown on cover slips in 6-well-plates, and the same procedures for cellular uptake experiment were followed but after incubation and washing, the cells were treated with FBS free medium and imaged using Leica TCS SP5 laser scanning confocal microscope (Leica microsystems Inc., Bensheim, Germany). LAS Af Lite 2.4.1 (Leica microsystems CMS GmbH) and FijiJ 1.44 (National Institute of Health, Bethesda MD) were used for image processing.

Synthesis of lysine-, DOTA-, and GPNMB-Fab-conjugated gemini surfactants

The synthesis of lysine-, DOTA-, and Fab-conjugated gemini surfactants are illustrated in Scheme 1. All reactions were carried out under a nitrogen atmosphere using standard Schlenk techniques. Mass spectra were obtained using a QSTAR XL MS/MS system. ^1H NMR spectra were recorded using a Bruker 500 MHz Avance spectrometer. Chemical shifts, δ , are reported in parts per million, referenced to the residual ^1H and ^{13}C (DMSO-d_6 at 2.50, 39.58), respectively. Purity of the compounds was further verified by reversed-phase (RP) HPLC (RP-HPLC) using an Agilent 1200 Series HPLC coupled to an UV detector and Waters 2796 HPLC System coupled to an UV and radiometric detector (Fig. S.1).

The synthesis of the $\text{N}_3\text{N}'\text{-}(((2\text{-aminoacetyl})\text{azanediyl})\text{bis}(\text{propane-3,1-diyl}))\text{bis}(\text{N,N-dimethylhexadecan-1-aminium})$ chloride (16-7NG-16) gemini surfactants used in this study have been previously described ²².

Synthesis of lysine-conjugated gemini surfactants

In step 1a, bis-boc-lysine, HATU, and DIPEA were sequentially placed in a 100-mL Schlenk flask containing 20 mL DMF at inert atmosphere to give a pale-yellow and later to a dark-red

1
2
3 mixture. After stirring for 15 min, 16-7NG-16 was added. DMF was removed under high vacuum
4
5 after stirring for 18 h. To the residue, 100 mL DCM was added and then extracted with saturated
6
7 sodium bicarbonate (5×100 mL). The extracted organic layer was dried over anhydrous sodium
8
9 sulfate, and concentrated under vacuum to give the reddish oily compound. In the next step (step
10
11 2b) the product was dissolved in 20 mL dry DCM followed by the addition of 10 mole equivalents
12
13 of HCl (4 M in dioxane). After stirring for 2 h, excess solvent was removed and the residue was
14
15 washed by decantation with diethyl ether. Finally, DCM was added to dissolve the compound and
16
17 then it was precipitated using diethyl ether. This was repeated three times before the sample was
18
19 dried under high vacuum. The final product 16-7NGK-16 had a yellowish to orange color.
20
21
22

23
24 16-7NGK-16: ^1H NMR (500 MHz, DMSO-d_6): δ = 8.93 (m) 1H, 8.44 (m) 3H, 8.27 (m) 3H, 4.15
25
26 (d) 1H, 4.04 (d) 1H, 3.90 (m) 1H, 3.33 (m) 12H, 3.04(s) 6H, 3.04 (s) 6H, 2.72 (m) 4H, 2.01 (m)
27
28 2H, 1.91 (m) 2H, 1.77 (m) 2H, 1.68–1.59 (m) 6H, 1.45 (m) 2H, 1.23 (m) 50H, 0.84 (t) 6H. MS-
29
30 TOF (m/z); calculated for $\text{C}_{50}\text{H}_{106}\text{N}_6\text{O}_2^{2+}$; expected 411.4183, found 411.4094.
31
32
33

34 **Synthesis of DOTA-conjugated gemini surfactants**

35
36
37 In step 2, 0.014 mmol of 16-7NG-16 was dissolved in 2 mL DMSO. After stirring for 15 min,
38
39 p-SCN-Bn-DOTA 0.014 mmol was added to the solution and the pH of the solution was adjusted
40
41 to 8.5 by adding DIPEA. The mixture was stirred for 24 hours. The solvent was removed under
42
43 vacuum and the product was separated by column chromatography (C18-reversed phase silica gel)
44
45 eluting with water/acetonitrile. The appropriate fraction was freeze dried to obtain the N,N'-(((2-
46
47 (3-(4-((1,4,7,10-tetracarboxy-1,4,7,10-tetraazacyclododecan-2-
48
49 yl)methyl)phenyl)thioureido)acetyl)azanediyl)bis(propane-3,1-diyl))bis(N,N-
50
51 dimethylhexadecan-1-aminium) chloride, 16-7NG-DOTA-16, DOTA modified gemini surfactant
52
53 solid product. The purity was further verified on RP-HPLC using Phenomenex Gemini-NX
54
55
56
57
58
59
60

(Phenomenex, United States) C18 analytical column (3 μ m, 4.6 mm X 150 mm). Gradient elution was performed at a flow rate of 1 mL/min using an Agilent 1200 Series HPLC system. Detection was performed using an Agilent absorbance detector at 254 nm. The mobile phase consisted of 0.1% trifluoroacetic acid in H₂O (solution A) and 0.1% trifluoroacetic acid in acetonitrile (solution B). The mobile phase was programmed as follows: gradient from 90 %A: 10 %B to 10 %A: 90 %B in 30 min.

16-7NG-DOTA-16: ¹H NMR (500 MHz, DMSO-d₆): δ = 7.52 (m) 2H, 7.26 (m) 2H, 4.40 (m) 2H, 3.43 m 25H, 3.24 (m) 9H, 2.99 (s) 6H, 3.03 (s) 6H, 2.55 (s) 3H, 2.04 (brs) 2H, 1.90 (brs) 2H, 1.65 (brs) 4H, 1.24 (m) 50H, 0.86 (t) 6H. MS-TOF (m/z); calculated for C₆₄H₁₁₉N₉O₉S ²⁺; expected 594.9420, found 594.9405.

Synthesis of GPNMB-Fab-conjugated gemini surfactants

In step 3, 0.144 mmol of 16-7NG-16 was dissolved in 10 mL DMSO. After stirring for 15 min, 0.144 mmol of NHS-PEG₁₀₀₀-COOH was added to the solution and the pH of the solution was adjusted to 8.5 by adding DIPEA. The mixture was stirred for 24 hours and the solvent was removed under high vacuum. In the final step (step 4) EDC (0.033 μ mol) and NHS (0.036 μ mol) were added to a solution of (0.028 μ mol) PEG₁₀₀₀-COOH conjugated gemini in 150 μ L DMF and the reaction mixture was stirred at room temperature for 2 h. The crude product was directly added to the 1 mL GPNMB-Fab solution (465 μ g/mL) in PBS and the mixture was stirred at 4°C for 30 min. The resulting protein solution was purified by centrifugal filtration (molecular weight cut-off, 10,000 Da) with PBS to obtain gemini-PEG₁₀₀₀-Fab (16-7NG-Fab-16).

Preparation of DOTA-gemini surfactant nanoparticles (DOTA-NP) and GPNMB-Fab-DOTA-gemini surfactant nanoparticles (Fab-DOTA-NP)

DOTA-gemini nanoparticles (DOTA-NP) were prepared by replacing 5 % of total gemini (16-NGK-16), that is 1 % of the total lipid content, in formula GNP1 with DOTA-conjugated gemini surfactant (16-NG-DOTA-16) during the preparation of the lipid film, and the same procedures for the preparation of gemini nanoparticles were followed. Fab-DOTA-NP were prepared by replacing 5 % (w/w) of gemini surfactant content in formula GNP1 (1 % w/w of total lipid composition) with DOTA-conjugated gemini surfactant (16-NG-DOTA-16) and 5% w/w of gemini surfactant in the formulation (1 % w/w of total lipid composition) by Fab-conjugated gemini surfactant (16-NG-Fab-16) (Table 1). To prepare Fab-DOTA-NP, Fab-PEG-gemini aqueous solution (0.4 mg/mL) was added dropwise with continuous stirring to 0.5 mL of nanoparticle dispersion. After an incubation time of 30 minutes at 37°C, the formula was stored at –80 °C. The particle size and zeta potential of targeted (Fab-DOTA-NP) and non-targeted (DOTA-NP) nanoparticles was determined as earlier described.

Fab-binding study using flow cytometry

GPNMB-Fab and Fab-DOTA-NP were labeled using Alexa Fluor[®] 647 (ex/em 650/668 nm) microscale protein labeling kit (Invitrogen, Eugene, OR, USA) according to the manufacturer's protocol. Melanoma-derived cell lines A375, G-361 and WM-115 (primary melanoma) and SH-4, SK-MEL-24 and RPMI-7951 (metastatic melanoma) were washed with PBS, detached using TrypLE[™] (gibco, USA), pelleted and resuspended in PBS at a final concentration of 2×10^6 cells/mL. One hundred microliters of cell suspension was incubated with 4.65 µg of labeled Fab, or the equivalent amount of labeled nanoparticles, for one hour at room temperature. After incubation, cells were washed with PBS, pelleted and resuspended in 500 µL PBS for FACS. To evaluate the non-specific binding, a control sample was prepared by incubating the cells with the same concentration of unlabeled GPNMB-Fab for half an hour, before adding the labeled Fab.

Radiolabeling and characterization of gemini surfactant nanoparticles

DOTA-NP and Fab-DOTA-NP were incubated with ^{111}In -acetate ($^{111}\text{InCl}_3/0.5\text{ M}$ ammonium acetate) for 1 hour at 37°C . The radiochemical purity (RCP) of ^{111}In -labeled nanoparticles was determined by instant thin layer chromatography (iTLC). Plates were developed in 20 mM sodium citrate ($\text{pH } 5.5$). ^{111}In -labeled DOTA-NP and ^{111}In -labeled Fab-DOTA-NP remained at the origin ($R_f = 0$), while free ^{111}In -acetate migrated with the solvent front ($R_f = 1$). The distribution of radioactivity in developed iTLC plates was determined using a automated gamma counter (2480 Wizard², PerkinElmer, Waltham MA). For stability evaluation, ^{111}In - DOTA-NP and ^{111}In - Fab-DOTA-NP were added to 0.5 mL PBS or mouse serum in $1:10$ volume ratio and were incubated at 37°C for 72 hours. At different time points, samples were taken from the stock solution and analyzed. Stability was evaluated using iTLC as described above.

In vitro binding and internalization

In vitro subcellular fractionation study was performed following the manufacturer's protocol (Nuclei EZ Prep Nuclei Isolation Kit; Sigma-Aldrich, Saint Louis, MO) with slight modification. RPMI-7951 cells were seeded in 6-well cluster plate at 4×10^5 cells per well the day prior to the assay and the medium was changed one hour prior to the assay. ^{111}In -labeled targeted (Fab-DOTA-NP. $5.5\text{ }\mu\text{M}$ GPNMB-Fab) and non-targeted (DOTA-NP) nanoparticles were added to the cells ($15\text{ }\mu\text{L}$, 0.25 MBq) and incubated in $5\text{ }\% \text{v/v}$ CO_2 humidified atmosphere at $37\text{ }^\circ\text{C}$ for 1, 2, 6 and 24 h. After incubation, cells were put on ice to stop internalization, washed twice with ice-cold PBS, detached with $0.25\text{ }\% \text{w/v}$ trypsin and the radioactivity was measured using a gamma counter. Thereafter, the cells were washed with acetate buffer ($\text{pH} = 2.6$) to strip nanoparticles bound to cell surface and were washed with PBS again and measured using a gamma counter. Finally, the cell suspension was vortexed and incubated in ice for 10 min in the presence of Nuclei EZ Lysis

1
2
3 Buffer for the isolation of nuclei from cells. The cells were then centrifuged for 5 min at 4 °C
4
5 where the supernatant collected contains the cytoplasmic fraction. The cells were then resuspended
6
7 again in Nuclei EZ Lysis Buffer, and the above procedure was repeated to collect the remaining
8
9 cytoplasmic fraction. The final pellet containing intact cell nuclei was counted using γ -counter to
10
11 determine the amount of ^{111}In .
12
13

14 15 **Pharmacokinetics of ^{111}In -DOTA-NP and ^{111}In -Fab-DOTA-NP**

16
17

18
19 Normal athymic CD-1 nude mice ($n = 4$) were injected intravenously via a tail vein with 4 – 5
20
21 MBq ^{111}In -DOTA-NP and ^{111}In -Fab-DOTA-NP. Blood samples were collected from a saphenous
22
23 vein at 5 min, 15 min, 30 min, 2, 4, 6, 24, 48 and 72 h post injection into a capillary tube. The
24
25 volume of the blood was determined by measuring the length of the blood sample in the capillary
26
27 tube using a digital caliper and converted to mL knowing the internal diameter of the capillary tube.
28
29 Thereafter, the radioactivity in the capillary tube was measured in a γ -counter and expressed as
30
31 percentage of the injected activity per mL (% IA/mL). Pharmacokinetic parameters were
32
33 calculated by fitting the blood radioactivity versus time to a two-compartment model using Prism
34
35 5.0 software (GraphPad). The area under the percentage of the injected activity per mL versus time
36
37 curves (AUC), clearance (CL), volume of distribution (V_{ss}), and half-lives ($t_{1/2\alpha}$, and $t_{1/2\beta}$) were
38
39 calculated.
40
41
42
43
44

45 **SPECT/CT imaging and biodistribution in mice**

46
47

48
49 Athymic CD-1 nude mice bearing G361 xenografts ($n = 4$) were injected via a tail vein with 15
50
51 – 17 MBq of ^{111}In -Fab-DOTA-NP or of ^{111}In -DOTA-NP. At 2, 24 and 48 hours after injection,
52
53 SPECT and CT images were acquired using MILabs Vector⁴CT scanner (MILabs B.V., Utrecht).
54
55 SPECT scans were acquired in a list-mode data format with a high-energy ultra-high resolution
56
57
58
59
60

(XUHS-M) mouse/rat pinhole collimator. Corresponding CT scans were acquired with a tube setting of 50 kV and 480 μ A. Images were reconstructed using a pixel-based order-subset expectation maximization (POS-EM) algorithm that included resolution recovery and compensation for distance-dependent pinhole sensitivity and were registered on CT and quantified using PMOD 3.8 software (PMOD, Switzerland). Tracer uptake was expressed as percentage injected activity (% IA) per volume (cc) of tissue volume (% IA/cc). All quantification data was reported as mean \pm standard deviation within one animal study group.

For biodistribution study, the animals were euthanized under deep anesthesia after the last imaging point and tissue samples including small intestine, stomach, lung, heart, muscle, liver, spleen, kidneys and tumor were harvested. Samples of selected tissues were excised and weighed and the amounts of radioactivity in tissue samples were measured using γ -counter. The radioactivity in the organs was expressed as percent injected activity per gram (% IA/g).

All animal experiments comply with the ARRIVE guidelines ²³ and were carried out in accordance the National Institutes of Health guide for the care and use of Laboratory animals National Research Council (US) Committee for the Update of the Guide for the Care and Use of Laboratory Animals, Guide for the Care and Use of Laboratory Animals, Guide for the Care and Use of Laboratory Animals, 2011 <<https://doi.org/10.17226/12910>>.. The study protocol was approved by Animal Research Ethics Board (AREB), University of Saskatchewan (protocol number 20150044).

Statistical analyses

All characterization experiments were performed in triplicates at the minimum and the results are expressed as mean values \pm standard deviation. Statistical analyses was evaluated by one-

way analysis of variance (ANOVA) followed by the Bonferroni post hoc test using SPSS version 23.0 (SPSS, IBM Company, Chicago, USA). Significant differences were considered at $p < 0.05$ values.

Results

Formulation and characterisation of gemini surfactant nanoparticles

Gemini surfactants nanoparticles were prepared using gemini surfactant (16-NGK-16), DOPE, DPPC and DSPC as helper lipids in different molar ratios (Table S.1). The prepared nanoparticles had a particle size ranging from 70 - 180 nm. The polydispersity index (PDI) of the nanoparticles was approximately 0.2 and the zeta potential ranged from 10 - 17 mV (see supplementary data). Formula GNP1 with particle size of 85.42 ± 0.68 nm (PDI 0.18 ± 0.01) and zeta potential of 17.07 ± 1.18 mV was chosen for DOTA and GPNMB Fab conjugation. TEM images (Fig. 1) show round particles less than 100 nm in diameter with no aggregations. The particle size of non-targeted gemini surfactant nanoparticles (DOTA-NP) and targeted gemini surfactant nanoparticles (Fab-DOTA-NP) was found to be 105.1 ± 2.98 nm (PDI 0.19 ± 0.0125) and 127.566 ± 2.45 (PDI 0.341 ± 0.0006), respectively. Based on the size of Fab-DOTA-NP and the mean molecular area of GPNMB-Fab-conjugated gemini surfactants ($a_0=7$)²², the number of GPNMB-Fab per one nanoparticle was calculated to be approximately 50.

Flow cytometry of gemini surfactant nanoparticles

The cellular uptake of gemini surfactant nanoparticles formula GNP1 was investigated in two melanoma cell lines, RPMI-7951 and A375 using flow cytometry. Two fluorescent dyes; the hydrophilic FITC-dextran and the hydrophobic DiO were used to label the nanoparticles. Flow cytometry showed that cells treated with dye solutions exhibited small or no shift in their

fluorescence compared to a significant shift observed with the fluorescent nanoparticles (Fig. 2), which was confirmed by confocal microscopy imaging (Fig. 3).

The binding of GPNMB-Fab conjugated nanoparticles in melanoma cell lines A375, G-361, WM-115, SH-4, SK-MEL-24 and RPMI-7951 was studied by flow cytometry (Fig.4). As a control, non-labeled antibody was used to block the receptors to study the specificity of binding. In case of RPMI-7951 cells, there was a remarkable shift in cell fluorescence in case of GPNMB-Fab-treated cells compared pre-blocked cells. In case of SH-4, the GPNMB-Fab treated cells and the pre-blocked cells were almost superimposed. The fluorescence shift in case of G361, SK-MEL-24 and A374 was less than that of RPMI-7951 but greater than for SH-4 cells. In order to investigate the effect of GPNMB-Fab conjugation with gemini surfactant nanoparticles on the binding to melanoma cells surface GPNMB receptors, the surface binding of Fab-DOTA-NP to two melanoma cell lines, namely, RPMI-7951 and A375 was investigated. There was no difference in fluorescence intensity between the unconjugated Fab and Fab-conjugated nanoparticles, indicating similar extent of binding at that concentration (Fig. 4 1b & 2b).

¹¹¹In-labeling and stability of DOTA-NP and Fab-DOTA-NP

The radiochemical purity in case of ¹¹¹In-labeled DOTA-NP was $97.6 \pm 1.7\%$ and in case of ¹¹¹In-labeled Fab-DOTA-NP was $98.2 \pm 1.6\%$, therefore, no further purification was needed. Stability of the ¹¹¹In labeled nanoparticles was studied in PBS and mouse serum using ITLC. No transchelation was observed for ¹¹¹In-DOTA-NP after 72 hours incubation in mouse serum and PBS, while ¹¹¹In-Fab-DOTA-NP showed a noticeable transchelation in mouse serum (3 %) and PBS (5.3 %). ¹¹¹In-DOTA-NP and ¹¹¹In-Fab-DOTA-NP were considered stable with only a small further increase in transchelation after one week incubation (Fig. S.2).

Intracellular distribution of ^{111}In -DOTA-NP and ^{111}In -Fab-DOTA-NP

We compared the *in vitro* intracellular distribution of non-targeted ^{111}In -DOTA-NP and GPNMB targeted ^{111}In -Fab-DOTA-NP (Fig. 5). Cell binding and intracellular uptake of targeted ^{111}In -Fab-DOTA-NP was significantly ($p < 0.05$) higher than for non-targeted ^{111}In -DOTA-NP at all time points. After one hour incubation 10.09 ± 1.40 % of ^{111}In -Fab-DOTA-NP was bound to RPMI cells versus 2.75 ± 0.71 % of ^{111}In -DOTA-NP ($p < 0.05$). Cell binding of nanoparticles peaked at six hours after incubation with 14.40 ± 2.33 % for ^{111}In -Fab-DOTA-NP compared to 4.42 ± 0.11 % for ^{111}In -DOTA-NP. Nuclear localization of GPNM targeted ^{111}In -Fab-DOTA-NP was more than 5-fold higher than ($p < 0.05$) for non-targeted ^{111}In -DOTA-NP (9.30 ± 2.11 % versus 1.85 ± 0.33 %).

Pharmacokinetics of ^{111}In -DOTA-NP and ^{111}In -Fab-DOTA-NP

The pharmacokinetics of targeted ^{111}In -Fab-DOTA-NP and non-targeted ^{111}In -DOTA-NP was studied in healthy athymic CD-1 mice. ^{111}In -Fab-DOTA-NP and ^{111}In -DOTA-NP followed a biphasic elimination. There was a significant difference ($p < 0.05$) in the pharmacokinetic parameters of ^{111}In -Fab-DOTA-NP ($\text{AUC} = 67.0 \pm 13.2$ % IA/mL \times h, $V_{ss} = 60.2 \pm 19.6$ mL, $\text{CL} = 1.22 \pm 0.21$ mL/h and distribution half-life $t_{1/2\alpha} = 0.6 \pm 0.5$ h) compared with ^{111}In -DOTA-NP ($\text{AUC} = 127.9 \pm 13.8$ % ID/mL \times h, $V_{ss} = 21.8 \pm 1.5$ mL and $\text{CL} = 0.8 \pm 0.1$ mL/h). There was no significant difference ($p > 0.05$) in the elimination half-life $t_{1/2\beta}$ of the GPNMB targeted ^{111}In -Fab-DOTA-NP (27.4 ± 3.6 h) compared with non-targeted ^{111}In -DOTA-NP (21.6 ± 2.1 h) (Fig. 6 and Table 2).

SPECT/CT imaging and biodistribution study in melanoma xenograft-bearing mice

Representative slices of microSPECT/CT images of a mouse bearing G361 melanoma xenograft injected with ^{111}In -Fab-DOTA-NP or ^{111}In -DOTA-NP at 2, 24 and 48 hours post

injection are shown (Fig. 7A & B). It is to be noted that RPMI-7951 cell line, which shows the greater binding affinity to GPNMB-Fab, was not used in the imaging studies because it did not develop subcutaneous xenograft in mice.

There was lower tumor uptake of the GPNMB targeted ^{111}In -Fab-DOTA-NP compared with non-targeted ^{111}In -DOTA-NP at all time points. The high activity uptake by the liver and spleen is another important observation for both targeted and non-targeted nanoparticles. Quantification of the decay-corrected images (Fig. 7C) confirmed significantly ($p < 0.05$) higher tumor uptake of non-targeted nanoparticles: 5.23 ± 0.55 , 5.77 ± 0.57 and 5.47 ± 0.46 %IA/cc at 2, 24 and 48 hours, compared with the targeted nanoparticles; $1.53 \pm .01$, 2.08 ± 0.36 and 1.87 ± 0.27 %IA/cc at the corresponding time points. *Ex vivo* biodistribution results were similar to the microSPECT imaging (Fig. 8). The highest activity accumulation was observed in the liver and spleen for both the targeted and non-targeted nanoparticles. For instance, spleen uptake of ^{111}In -Fab-DOTA-NP was 84.45 ± 26.20 versus 30.72 ± 2.88 %IA/g for ^{111}In -DOTA-NP. On the other hand liver uptake for the targeted nanoparticles (10.09 ± 4.84 %IA/g) was significantly lower than that of the non-targeted nanoparticles (21.32 ± 1.26 %IA/g). Significantly higher uptake ($p < 0.05$) was seen in the lung, heart, skin and brain for the non-targeted ^{111}In -DOTA-NP compared with the GPNMB targeted ^{111}In -Fab-DOTA-NP. *Ex vivo* biodistribution also confirmed higher tumor ($p < 0.05$) uptake of non-targeted ^{111}In -DOTA-NP (4.31 ± 0.40 %IA/g) compared with ^{111}In -Fab-DOTA-NP (1.37 ± 0.18 %IA/g) at 48 hours post injection.

Discussion

Gemini surfactants assemble spontaneously into complex supramolecular structures (micelles, bilayers and vesicles) 1000-fold more efficiently compared to their monovalent analogues²⁵. The

low critical micelle concentration (CMC) is beneficial to minimize the amount of gemini surfactant needed in the formulation process, which in turn ensures an optimal safety profile and reduces the cost of the delivery system ²⁶. Cancerous cells overexpress the negatively charged phosphatidylserine on the cell membrane compared to normal tissues. Previous research results have found that human melanoma cells express a higher level phosphatidylserine compared to other cancer types ²⁷. This adds additional advantage to gemini surfactants nanoparticles, with cationic head groups, as a delivery system for cancer cells and specifically melanoma.

In the present study lipid film hydration method was applied to prepare gemini surfactant-based nanoparticles by the aid of DOPE, DPPC or DSPC. The particle size of the nanoparticles fell in the range of 50-200 nm, which is optimal for cellular uptake ²⁸. Polydispersity index of the prepared formulae was ≤ 0.2 indicating narrow range of particle size distribution ²⁹ (Table S.1). To study the cellular uptake of the gemini surfactant nanoparticles, two fluorescent dyes were loaded to the nanoparticles; the hydrophilic FITC-dextran ($\log p = 2$) ³⁰ and the hydrophobic DiO ($\log p = 5$) ³¹, and the cellular uptake was examined using flow cytometry (Fig. 2). It is clear that FITC-dextran and DiO are not taken up by the cells unless they are incorporated with the nanoparticles. Similar results could be seen in confocal microscopic images (Fig. 3) of cells internalising fluorescent nanoparticles while those treated with dye solutions exhibited little or almost no fluorescence.

Active targeting of nanoparticles with monoclonal antibodies can enhance their uptake by cancer cells that over express the target antigen ³². Fab fragment-modified nanoparticles exhibit longer systemic circulation than those modified with whole immunoglobulin G since reticuloendothelial system uptakes nanoparticles via the Fc receptor-mediated mechanism ^{33,34}. GPNMB is a glycosylated transmembrane protein that is overexpressed in melanoma among other

types of cancer³⁵. Anti-GPNMB antibody Fab fragment (GPNMB-Fab) was chosen as a targeting moiety. To understand the binding affinity of GPNMB-Fab to melanoma, six melanoma cell lines were screened by flow cytometry (Fig. 4). The cell lines were selected to represent different types of melanoma tumors and variable degrees of GPNMB antigen expression as reported in the literature. Three primary melanoma cell lines; A375, G-361 and WM-115, and three metastatic melanoma cells SH-4, SK-MEL-24 and RPMI-7951 have been investigated. RPMI-7951, G361 and SK-MEL-24 are reported to be highly expressing GPNMB antigen¹¹, A375 weakly expresses the antigen³⁶, whereas, WM-115 and SH4 had not been tested before. The results showed that the degree of cellular binding depends on the level of antigen expression. RPMI-7951 cells showed the highest binding affinity among the cell lines tested, SH4 exhibited the lowest binding capacity, and the rest of the cell lines showed intermediate affinity compared to these two cell lines.

To formulate gemini surfactant nanoparticles radiolabeled with ¹¹¹In and actively targeted with GPNMB-Fab, DOTA-conjugated gemini surfactant (16-7NG-DOTA-16) and Fab-conjugated gemini surfactant (16-7NG-Fab-16) were synthesized and characterised by mass spectroscopy, ¹H NMR and RP-HPLC (Fig. S.1). Flow cytometry was used to confirm that conjugation did not affect binding to cells. Subcellular fractionation experiment was carried out to investigate the intracellular fate of ¹¹¹In-labeled targeted (¹¹¹In-Fab-DOTA-NP) and non-targeted (¹¹¹In-DOTA-NP) nanoparticles (Fig. 5). Over 24 hours, the surface binding and nuclear uptake of the targeted nanoparticle was significantly higher than the non-targeted nanoparticles. This indicates that GPNMB-Fab targeted nanoparticles can be more effective than non-targeted nanoparticles at releasing cytotoxic payloads to the vicinity of the nucleus of melanoma cancer cells where they can cause enhanced DNA damage and hence cell death³⁷.

As observed in the pharmacokinetic parameters, the AUC of the Fab-targeted nanoparticles ($67.0 \pm 13.2\%$ IA hr/mL) is about half that of the non-targeted nanoparticles ($127.9 \pm 13.8\%$ IA hr/mL) which indicates that less of the targeted formulation was circulation for efficient tumor uptake. Similarly, the volume of distribution of the targeted nanoparticles (60.2 ± 19.6 mL) was almost three times greater than non-targeted nanoparticles (21.8 ± 1.5 mL) which reflects the high spleen uptake of the targeted nanoparticles. SPECT/CT imaging showed that tumor uptake in case of non-targeted nanoparticles was greater than the targeted nanoparticles (Fig. 7C), with maximum uptake at 24 hours. By decay corrected quantification of images, a significant difference in the radioactivity was detected between the targeted and non-targeted nanoparticles, with the greatest uptake ($5.77 \pm 0.57\%$ IA/cc) at 24 hours for the non-targeted nanoparticles. The main mechanism of targeting nanoparticulate delivery systems is passive targeting derived by the EPR effect which is due to the leaky vasculature and the poor lymphatic drainage of tumors³⁸. The physicochemical properties of the nanoparticles such as the particle size, surface charge in addition to the tumor microenvironment, all determine the extent of nanoparticles extravasation to the tumor³⁹. In our study, the non-targeted and targeted nanoparticles have the optimal size for tumor uptake (105.1 ± 2.0 and 127.6 ± 2.5 nm, respectively). Besides, the positive surface charge imparted by gemini surfactant is favorable for tumor cells binding and uptake, as shown by flow cytometry and cell fractionation studies. Similar tumor uptake ($< 7\%$ IA/cc) was shown for ¹¹¹In-labeled liposomes in ovarian cancer xenografts⁴⁰.

It is difficult to predict the *in vivo* behavior of targeted nano-delivery systems. Some studies have shown that conjugation of a targeting group improves tumor uptake while others have shown that it does not improve tumor uptake^{41 42}. A number of studies have shown that the active targeting of nanoparticle to epidermal growth factor receptors such as Her1/EGFR, and Her2 using

ligands such as the epidermal growth factor (EGF) peptide and anti-Her2 monoclonal antibody fragments (Fab or single chain Fv) did not result in increased tumor uptake ^{43,44}. In this regard, Kirpotin *et al* showed that active targeting of liposome with anti-Her2 monoclonal antibody fragment did not lead to an increase in tumor uptake when compared with the non-targeted formulation ⁴⁵. In another study, Fonge *et al* showed that tumor uptake of the non-targeted block copolymer micelles was significantly higher than that of EGF-targeted micelles in a breast cancer xenograft model ⁴⁶. They also found that decreasing the density of the targeting moiety from 5 mol% to 1 mol% resulted in improved tumor uptake. In the same context, a novel anti-EphA2 targeted docetaxel antibody directed nanotherapeutic was formulated with 15 scFv / liposome compared to 50 GPNMB-Fab fragments per nanoparticles in our study ^{47,48}. In addition, the rapid blood clearance and high spleen uptake of the GPNMB targeted nanoparticles can be accounted for its low tumor uptake. In our case the lower tumor uptake of GPNMB targeted nanoparticles can be improved by further optimization of the formulation.

Conclusion

¹¹¹In-labeled gemini surfactant-based nanoparticles were successfully optimized with respect to the particle size and surface charge to be optimal for endocytic internalization by tumor cells with minimal loss of ¹¹¹In in mouse serum and PBS upon incubation for one week. In a melanoma xenograft model, promising results are shown with the non-targeted formulation compared with GPNMB-targeted ones. One approach to improve tumor uptake of GPNMB targeted NP is to optimize the density of anti-GPNM Fab on the surface of the nanoparticles, as well as other physiochemical characteristics of the nano-delivery system.

Acknowledgment

This work was funded by Sylvia Fedoruk Canadian Centre for Nuclear Innovation (J2014/002, Imaging gene delivery nanoparticles targeted to melanoma), and Saskatchewan Health Research Foundation grant no. 3350 (Development of theranostic agents for melanoma). We also thank Waleed Mohammed-Saeid for his help in formulation development.

Disclosure

The author reports no conflicts of interest in this work.

Supporting information

Supporting information is available for Table S.1, Fig. S.1, and Fig. S.2. Material for chemical synthesis of compounds, formulation and characterization of gemini nanoparticles and cell culture are also available in the supporting data.

References

- (1) Canadian Cancer Statistics Advisory Committee. Canadian Cancer Statistics; A 2018 Special Report on Cancer Incidence by Stage. Toronto, Can. Cancer Soc. 2018.
- (2) Wolchok, J. How Recent Advances in Immunotherapy Are Changing the Standard of Care for Patients with Metastatic Melanoma. *Ann. Oncol.* 2012, 23 (Suppl 8), viii15-21.
- (3) Gandhi, L.; Vansteenkiste, J. F.; Shepherd, F. A. 50 - Immunotherapy and Lung Cancer. In *IASLC Thoracic Oncology (Second Edition)*; Harvey I. Pass, D. B. and G. V. S., Ed.; Philadelphia, 2018; p 501.
- (4) Chen, J.; Shao, R.; Zhang, X. D.; Chen, C. Applications of Nanotechnology for Melanoma Treatment, Diagnosis, and Theranostics. *Int. J. Nanomedicine* 2013, 8, 2677–2688.
- (5) Loo, Y.; Grigsby, C. L.; Yamanaka, Y. J.; Chellappan, M. K.; Jiang, X.; Mao, H. Q.;

- Leong, K. W. Comparative Study of Nanoparticle-Mediated Transfection in Different GI Epithelium Co-Culture Models. *J. Control. Release* 2012, 30 (160), 48–56.
- (6) Li, J.; Wang, Y.; Liang, R.; An, X.; Wang, K.; Shen, G.; Tu, Y.; Zhu, J.; Tao, J. Recent Advances in Targeted Nanoparticles Drug Delivery to Melanoma. *Nanomedicine Nanotechnology, Biol. Med.* 2015, April, 769–794.
- (7) Kenny, G. D.; Villegas-Llerena, C.; Tagalakakis, A. D.; Campbell, F.; Welser, K.; Botta, M.; Tabor, A. B.; Hailes, H. C.; Lythgoe, M. F.; Hart, S. L. Multifunctional Receptor-Targeted Nanocomplexes for Magnetic Resonance Imaging and Transfection of Tumours. *Biomaterials* 2012, 33 (29), 7241–7250.
- (8) Singh, J.; Yang, P.; Michel, D.; Verrall, R. E.; Foldvari, M.; Badea, I. Amino Acid-Substituted Gemini Surfactant-Based Nanoparticles as Safe and Versatile Gene Delivery Agents. *Curr. Drug Deliv.* 2011, 8 (3), 299–306.
- (9) Yang, P.; Singh, J.; Wettig, S.; Foldvari, M.; Verrall, R. E.; Badea, I. Enhanced Gene Expression in Epithelial Cells Transfected with Amino Acid-Substituted Gemini Nanoparticles. *Eur. J. Pharm. Biopharm.* 2010, 75, 11–20.
- (10) Singh, J.; Michel, D.; Getson, H. M.; Chitanda, J. M.; Verrall, R. E.; Badea, I. Development of Amino Acid Substituted Gemini Surfactant-Based Mucoadhesive Gene Delivery Systems for Potential Use as Noninvasive Vaginal Genetic Vaccination. *Nanomedicine* 2015, 10 (3), 405–417.
- (11) Tse, K. F.; Jeffers, M.; Pollack, V. A.; McCabe, D. A.; Shadish, M. L.; Khramtsov, N. V.; Hackett, C. S.; Shenoy, S. G.; Kuang, B.; Boldog, F. L.; et al. CR011, a Fully Human Monoclonal Antibody-Auristatin E Conjugate, for the Treatment of Melanoma. *Clin.*

- Cancer Res. 2006, 15 (12), 1373–1382.
- (12) Rose, A. A. N.; Grosset, A.; Dong, Z.; Russo, C.; Macdonald, P. A.; Bertos, N. R.; St-Pierre, Y.; Simantov, R.; Hallett, M.; Park, M.; et al. Glycoprotein Nonmetastatic B Is an Independent Prognostic Indicator of Recurrence and a Novel Therapeutic Target in Breast Cancer. *Clin. Cancer Res.* 2010, 16 (7), 2147–2156.
- (13) Rose, A. A. N.; Biondini, M.; Curiel, R.; Siegel, P. M. Targeting GPNMB with Glembatumumab Vedotin: Current Developments and Future Opportunities for the Treatment of Cancer. *Pharmacol. Ther.* 2017, Nov (179), 127–141.
- (14) Rose, A. A. N.; Annis, M. G.; Dong, Z.; Pepin, F.; Hallett, M.; Park, M.; Siegel, P. M. ADAM10 Releases a Soluble Form of the GPNMB/Osteoactivin Extracellular Domain with Angiogenic Properties. *PLoS One* 2010, 5 (8), e12093.
- (15) Ott, P. A.; Hamid, O.; Pavlick, A. C.; Kluger, H.; Kim, K. B.; Boasberg, P. D.; Simantov, R.; Crowley, E.; Green, J. A.; Hawthorne, T.; et al. Phase I/II Study of the Antibody-Drug Conjugate Glembatumumab Vedotin in Patients With Advanced Melanoma. *J. Clin. Oncol.* 2014, 32 (32), 3659–3666.
- (16) Yardley, D. A.; Weaver, R.; Melisko, M. E.; Saleh, M. N.; Arena, F. P.; Forero, A.; Cigler, T.; Stopeck, A.; Citrin, D.; Oliff, I.; et al. EMERGE: A Randomized Phase II Study of the Antibody-Drug Conjugate Glembatumumab Vedotin in Advanced Glycoprotein NMB–Expressing Breast Cancer. *J. Clin. Oncol.* 2015, 33 (14), 1609–1619.
- (17) Ott, P. A.; Pavlick, A. C.; Johnson, D. B.; Hart, L. L.; Infante, J. R.; Luke, J. J.; Lutzky, J.; Rothschild, N. E.; Spitler, L. E.; Cowey, C. L.; et al. A Phase II Study of Glembatumumab Vedotin (GV), an Antibody-Drug Conjugate (ADC) Targeting GpNMB, in Advanced

- Melanoma. *J. Clin. Oncol.* 2017, 35 (15_suppl), 109.
- (18) Celldex Therapeutics. Celldex's METRIC Study in Metastatic Triple-Negative Breast Cancer Does Not Meet Primary Endpoint.
<http://ir.celldex.com/releasedetail.cfm?ReleaseID=1063842> 2018, last accessed on 4/23/2018.
- (19) Liu, Y.; Fang, J.; Joo, K. Il; Wong, M. K.; Wang, P. Codelivery of Chemotherapeutics via Crosslinked Multilamellar Liposomal Vesicles to Overcome Multidrug Resistance in Tumor. *PLoS One* 2014, 10 (3), e110611.
- (20) Chattopadhyay, N.; Fonge, H.; Cai, Z.; Scollard, D.; Lechtman, E.; Done, S. J.; Pignol, J. P.; Reilly, R. M. Role of Antibody-Mediated Tumor Targeting and Route of Administration in Nanoparticle Tumor Accumulation in Vivo. *Mol. Pharm.* 2012, 9 (8), 2168–2179.
- (21) Elgqvist, J.; Frost, S.; Pouget, J.-P.; Albertsson, P. The Potential and Hurdles of Targeted Alpha Therapy – Clinical Trials and Beyond. *Front. Oncol.* 2014, 3 (324), 1–9.
- (22) Al-Dulaymi, M. A.; Chitanda, J. M.; Mohammed-Saeid, W.; Araghi, H. Y.; Verrall, R. E.; Grochulski, P.; Badea, I. Di-Peptide-Modified Gemini Surfactants as Gene Delivery Vectors: Exploring the Role of the Alkyl Tail in Their Physicochemical Behavior and Biological Activity. *AAPS J.* 2016, 18 (5), 1168–1181.
- (23) Kilkenny, C.; Browne, W.; Cuthill, I. C.; Emerson, M.; Altman, D. G. Animal Research: Reporting in Vivo Experiments: The ARRIVE Guidelines. *Br. J. Pharmacol.* 2010, 160 (7), 1577–1579.
- (24) Guide for the Care and Use of Laboratory Animals, National Research Council (US)

- Committee for the Update of the Guide for the Care and Use of Laboratory Animals., 8th ed.; National Academies Press (US): Washington (DC), 2011.
- (25) Kirby, A. J.; Camilleri, P.; Engberts, J. B. F. N.; Feiters, M. C.; Nolte, R. J. M.; Söderman, O.; Bergsma, M.; Bell, P. C.; Fielden, M. L.; García Rodríguez, C. L.; et al. Gemini Surfactants: New Synthetic Vectors for Gene Transfection. *Angew. Chemie Int. Ed.* 2003, 42 (13), 1448–1457.
- (26) Menger, F. M.; Littau, C. A. Gemini-Surfactants: Synthesis and Properties. *J. Am. Chem. Soc.* 1991, 113 (4), 1451–1452.
- (27) Riedl, S.; Rinner, B.; Asslaber, M.; Schaidler, H.; Walzer, S.; Novak, A.; Lohner, K.; Zweglick, D. In Search of a Novel Target - Phosphatidylserine Exposed by Non-Apoptotic Tumor Cells and Metastases of Malignancies with Poor Treatment Efficacy. *Biochim. Biophys. Acta - Biomembr.* 2011, 1808 (11), 2638–2645.
- (28) Davis, M. E.; Chen, Z.; Shin, D. M. Nanoparticle Therapeutics: An Emerging Treatment Modality for Cancer. *Nat. Rev. Drug Discov.* 2008, 7 (9), 771–782.
- (29) Michel, D.; Chitanda, J. M.; Balogh, R.; Yang, P.; Singh, J.; Das, U.; El-Aneed, A.; Dimmock, J.; Verrall, R.; Badea, I. Design and Evaluation of Cyclodextrin-Based Delivery Systems to Incorporate Poorly Soluble Curcumin Analogs for the Treatment of Melanoma. *Eur. J. Pharm. Biopharm.* 2012, 81 (3), 548–556.
- (30) Hoffmann, A.; Bredno, J.; Wendland, M.; Derugin, N.; Ohara, P.; Wintermark, M. High and Low Molecular Weight Fluorescein Isothiocyanate (FITC)-Dextran to Assess Blood-Brain Barrier Disruption: Technical Considerations. *Transl. Stroke Res.* 2011, 2 (1), 106–111.

- (31) Tibor Cserháti. Liquid Chromatography of Natural Pigments and Synthetic Dyes, 1st ed.; Elsevier: Amsterdam, 2007.
- (32) Carter, T.; Mulholland, P.; Chester, K. Antibody-Targeted Nanoparticles for Cancer Treatment. *Immunotherapy* 2016, 8 (8), 941–958.
- (33) Maruyama, K.; Ishida, O.; Takizawa, T.; Moribe, K. Possibility of Active Targeting to Tumor Tissues with Liposomes. *Adv. Drug Deliv. Rev.* 1999, 40 (1), 89–102.
- (34) Kang, D. Il; Lee, S.; Lee, J. T.; Sung, B. J.; Yoon, J. Y.; Kim, J. K.; Chung, J.; Lim, S. J. Preparation and in Vitro Evaluation of Anti-VCAM-1-Fab'-Conjugated Liposomes for the Targeted Delivery of the Poorly Water-Soluble Drug Celecoxib. *J. Microencapsul.* 2011, 28 (3), 220–227.
- (35) Rose, A. A. N.; Annis, M. G.; Frederick, D. T.; Biondini, M.; Dong, Z.; Kwong, L.; Chin, L.; Keler, T.; Hawthorne, T.; Watson, I. R.; et al. MAPK Pathway Inhibitors Sensitize BRAF-Mutant Melanoma to an Antibody-Drug Conjugate Targeting GPNMB. *Clin. Cancer Res.* 2016, 22 (24), 6088–6098.
- (36) Qian, X.; Mills, E.; Torgov, M.; LaRochelle, W. J.; Jeffers, M. Pharmacologically Enhanced Expression of GPNMB Increases the Sensitivity of Melanoma Cells to the CR011-VcMMAE Antibody-Drug Conjugate. *Mol. Oncol.* 2008, 2 (1), 81–93.
- (37) Zustovich, F.; Barsanti, R. Targeted α Therapies for the Treatment of Bone Metastases. *Int. J. Mol. Sci.* 2017, 19 (74), 1–12.
- (38) Shargh, V. H.; Hondermarck, H.; Liang, M. Antibody-Targeted Biodegradable Nanoparticles for Cancer Therapy. *Nanomedicine* 2016, 11 (1), 63–79.
- (39) Shi, J.; Kantoff, P. W.; Wooster, R.; Farokhzad, O. C. Cancer Nanomedicine: Progress,

- Challenges and Opportunities. *Nat. Rev. Cancer* 2017, 17 (1), 20–37.
- (40) Ito, K.; Hamamichi, S.; Asano, M.; Hori, Y.; Matsui, J.; Iwata, M.; Funahashi, Y.; Umeda, I. O.; Fujii, H. Radiolabeled Liposome Imaging Determines an Indication for Liposomal Anticancer Agent in Ovarian Cancer Mouse Xenograft Models. *Cancer Sci.* 2016, 107 (1), 60–67.
- (41) Colombo, I.; Overchuk, M.; Chen, J.; Reilly, R. M.; Zheng, G.; Lheureux, S. Molecular Imaging in Drug Development: Update and Challenges for Radiolabeled Antibodies and Nanotechnology. *Methods* 2017, 130, 23–35.
- (42) Pirollo, K. F.; Chang, E. H. Does a Targeting Ligand Influence Nanoparticle Tumor Localization or Uptake? *Trends Biotechnol.* 2008, 26 (10), 552–558.
- (43) Lee, H.; Fonge, H.; Hoang, B.; Reilly, R. M.; Allen, C. The Effects of Particle Size and Molecular Targeting on the Intratumoral and Subcellular Distribution of Polymeric Nanoparticles. *Mol. Pharm.* 2010, 7 (4), 195–208.
- (44) Hoang, B.; Ekdawi, S. N.; Reilly, R. M.; Allen, C. Active Targeting of Block Copolymer Micelles with Trastuzumab Fab Fragments and Nuclear Localization Signal Leads to Increased Tumor Uptake and Nuclear Localization in HER2-Overexpressing Xenografts. *Mol. Pharm.* 2013, 10 (11), 4229–4241.
- (45) Kirpotin, D. B.; Drummond, D. C.; Shao, Y.; Shalaby, M. R.; Hong, K.; Nielsen, U. B.; Marks, J. D.; Benz, C. C.; Park, J. W. Antibody Targeting of Long-Circulating Lipidic Nanoparticles Does Not Increase Tumor Localization but Does Increase Internalization in Animal Models. *Cancer Res.* 2006, 66 (13), 6732–6740.
- (46) Fonge, H.; Huang, H.; Scollard, D.; Reilly, R. M.; Allen, C. Influence of Formulation

Variables on the Biodistribution of Multifunctional Block Copolymer Micelles. *J. Control. Release* 2012, 157 (3), 366–374.

(47) Geddie, M. L.; Kohli, N.; Kirpotin, D. B.; Razlog, M.; Jiao, Y.; Kornaga, T.; Rennard, R.; Xu, L.; Schoerberl, B.; Marks, J. D.; et al. Improving the Developability of an Anti-EphA2 Single-Chain Variable Fragment for Nanoparticle Targeting. *MAbs* 2017, 9 (1), 58–67.

(48) Kirpotin, D. B.; Tipparaju, S.; Huang, Z. R.; Kamoun, W. S.; Pien, C.; Kornaga, T.; Oyama, S.; Olivier, K.; Marks, J. D.; Koshkaryev, A.; et al. Abstract 3912: MM-310, a Novel EphA2-Targeted Docetaxel Nanoliposome. *Cancer Res.* 2016, 76 (14 Supplement), 3912.

Figure legends

Scheme 1. Synthesis of (1) 16-7NGK-16; (2) 16-7NG-DOTA-16 and (3) 16-7NG-Fab-16. Step 1a: bis-boc-lysine, HATU, DIPEA, DMF, 18 h. Step 1b: 4 M HCl, dichloromethane, 2 h. (2) p-SCN-Bn-DOTA, DIPEA, DMSO, 24 h. Step 3a: NHS-PEG₁₀₀₀-COOH, DIPEA, DMSO, 24 h. Step 3b: Fab, EDC, NHS, DMF, 3 h.

Fig. 1. Transmission electron microscope (TEM) images of gemini surfactant nanoparticles formula GNP1 before and after lyophilisation.

Fig. 2. Cellular uptake of gemini surfactant nanoparticles in (1) RPMI-7951 and (2) A375 melanoma cells using flow cytometry: a) gemini surfactant nanoparticles loaded with FITC-dextran and b) gemini surfactant nanoparticles loaded with DiO compared with dye solutions.

Fig. 3. Confocal microscopy images of RPMI-7951 cells (40×) treated with DiO labeled nanoparticles (1), DiO solution (2), FITC-dextran nanoparticles (3) and FITC-dextran solution (4); bright field (a), green filter (b) and merge(c)

Fig. 4. Flow cytometry analysis of GPNMB positive and negative cell lines. 1a) binding of unconjugated anti-GPNMB Fab to GPNMB positive RPMI-795 cells, 1b) binding of anti-GPNMB Fab nanoparticles to RPMI-795 cells; 2a) binding of unconjugated anti-GPNMB Fab to GPNMB positive A375 cells, 2b) binding of anti-GPNMB Fab nanoparticles to GPNMB positive A375

cells.. Binding of anti-GPNMB Fab to 3) WM115, 4) SK-MEL-24, 5) G361 and 6) SH4 (6) melanoma cell lines is shown. NP = nanoparticle

Fig. 5. *In vitro* subcellular distribution of non-targeted ^{111}In -DOTA-NP and targeted ^{111}In -Fab-DOTA-NP in RPMI-7951 melanoma cells. Cancer cells were incubated for 1, 2, 6 and 24 h prior to subcellular fractionation. Gamma counting was performed for quantification of ^{111}In -labeled nanoparticles in each subcellular fraction (n = 3)

Fig. 6. Pharmacokinetic profile of ^{111}In -Fab-DOTA-NP and ^{111}In -DOTA-NP in athymic CD-1 nude mice bearing G361 xenografts (Error bars present standard deviation, n = 4).

Fig. 7. Representative microSPECT/CT images of ^{111}In -Fab-DOTA-NP (A) and ^{111}In -DOTA-NP (B) in mice bearing G361 melanoma xenograft at 2, 24 and 48 hours post injection. Red cycles indicate tumor, C) Tumor accumulation of ^{111}In -Fab-DOTA-NP and ^{111}In -DOTA-NP by microSPECT/CT decay corrected image analysis. (Error bars present standard deviation, n = 4, * p < 0.05)

Fig. 8. Biodistribution of ^{111}In -Fab-DOTA-NP and ^{111}In -DOTA-NP in athymic CD-1 nude mice bearing G361 xenograft at 48 hours after intravenous injection (Error bars present standard deviation, n = 4, * p < 0.05)


Table 1. Composition (presented as % w/w of total lipid) of the DOTA-gemini surfactant nanoparticles (DOTA-NP) and GPNMB-Fab-DOTA-gemini surfactant nanoparticles (Fab-DOTA-NP).

	Fab-conjugated gemini surfactant (16-NG-Fab-16)	DOTA-conjugated gemini surfactant (16-NG-DOTA- 16)	Gemini surfactant (16-7NG-16)	1, 2 dioleoyl- <i>sn</i> -glycero- phosphatidylethanolamine (DOPE)
DOTA-gemini surfactant nanoparticles (DOTA-NP)	-	1%	19%	80%
Fab-conjugated gemini surfactant (16-NG-Fab-16)	1%	1%	18%	80%

Table 2. Pharmacokinetic parameters of ¹¹¹In-DOTA-NP and ¹¹¹In-Fab-DOTA-NP.


Formulation	AUC [†] (% IA hr/mL)	V _{ss} [†] (mL)	Cl [†] (mL/h)	t _{1/2α} [†] (h)	t _{1/2β} (h)
¹¹¹ In-Fab-DOTA-NP	67.0 ± 13.2	60.2 ± 19.6	1.5 ± 0.3	0.6 ± 0.5	27.4 ± 3.6
¹¹¹ In-DOTA-NP	127.9 ± 13.8	21.8 ± 1.5	0.8 ± 0.1	1.3 ± 0.4	21.6 ± 2.1

[†] The difference between ¹¹¹In-Fab-DOTA-NP and ¹¹¹In-DOTA-NP was significant (*p* < 0.05)

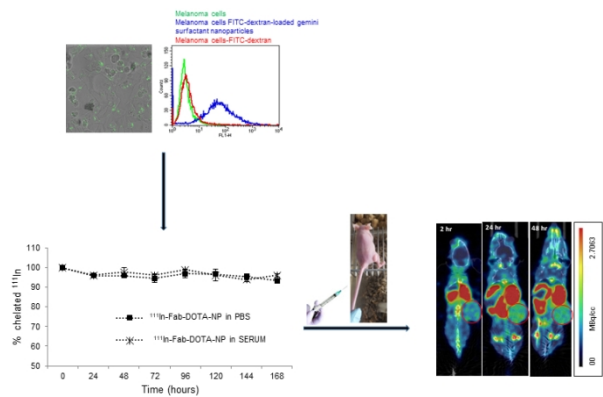

Graphical abstract

338x190mm (96 x 96 DPI)

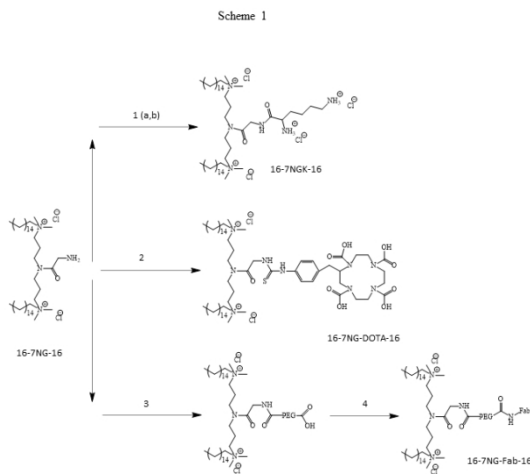

Scheme 1

338x190mm (96 x 96 DPI)

Fig. 1

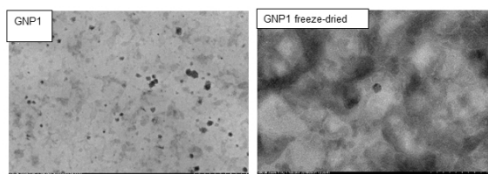


Fig. 1

338x190mm (96 x 96 DPI)

Fig. 2

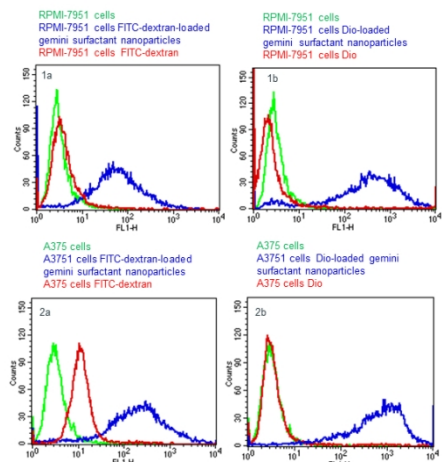


Fig. 2

338x190mm (96 x 96 DPI)

Fig. 3

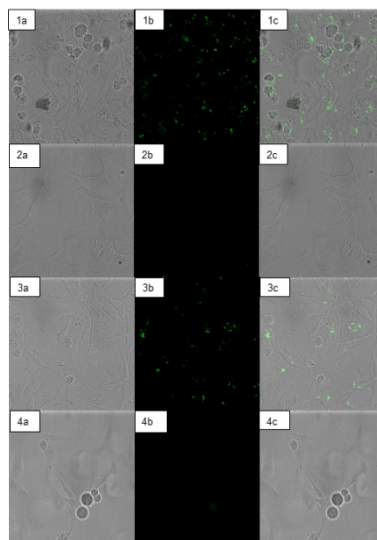


Fig. 3

338x190mm (96 x 96 DPI)

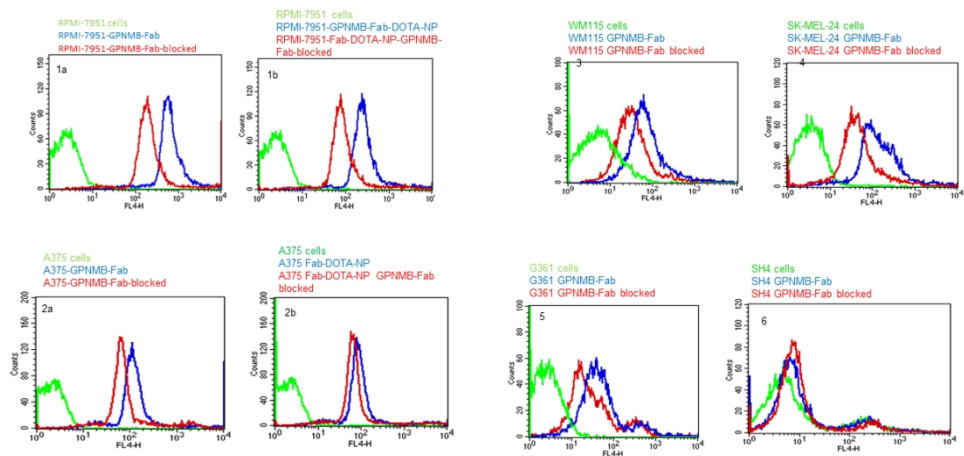


Fig. 4

338x190mm (96 x 96 DPI)

Fig. 5

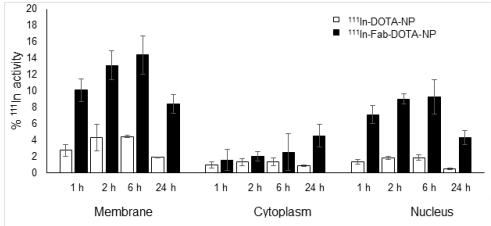


Fig. 5

338x190mm (96 x 96 DPI)

Fig. 6

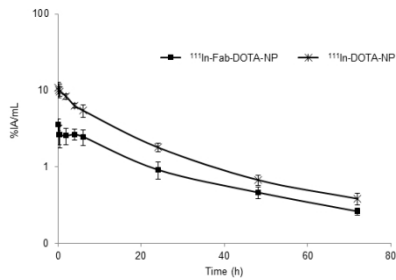


Fig. 6

338x190mm (96 x 96 DPI)

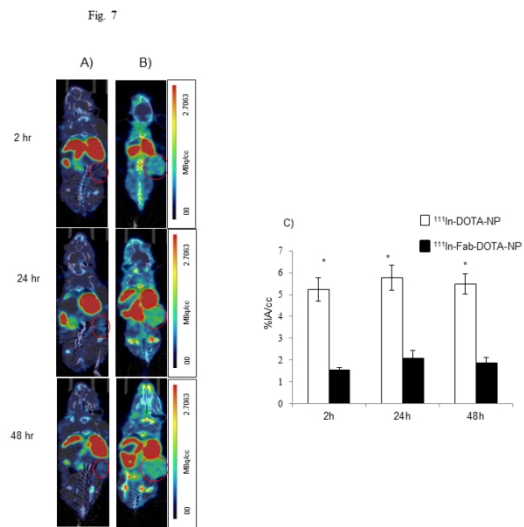


Fig. 7

338x190mm (96 x 96 DPI)

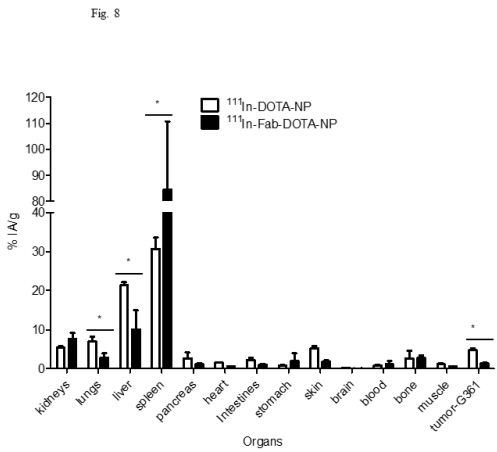


Fig. 8

338x190mm (96 x 96 DPI)